

Volume Changes on Melting for Several Rare Earth Chlorides

K. Igarashi and J. Mochinaga

Department of Synthetic Chemistry, Faculty of Engineering, Chiba University, Chiba-shi, Chiba 260, Japan

Z. Naturforsch. **42a**, 777–778 (1987);
received March 25, 1987

Molar volumes in the liquid state and melting points of several rare earth chlorides RCl_3 ($\text{R} = \text{La}$, Pr , Nd , Gd , Dy , and Y) have been measured by dilatometry and DTA, respectively. The volume changes on melting of these chlorides were evaluated on the basis of these result and available crystal structure data. The volume increase on melting of the hexagonal chlorides from LaCl_3 to GdCl_3 was found to be more than 20%. On the other hand, the volume changes of the monoclinic DyCl_3 and YCl_3 were less than 1%.

The volume change on melting gives information about the structure of a melt. For the alkali metal halides, the relationship between the volume change on melting and the short range arrangement of the melt near the melting point has been expressed by a semi-empirical formula by Furukawa [1]. Data on melting points of rare earth chlorides have been reported [2–9], but there are some uncertainties due to their strong hygroscopy. In this work, in order to determine exactly the volume changes on melting of LaCl_3 , PrCl_3 , NdCl_3 , GdCl_3 , DyCl_3 , and YCl_3 , their molar volumes in the liquid state and their melting points were measured while their molar volumes in the solid state were calculated on the basis of available crystal structure data [10–12].

The salts were prepared by reaction of the rare earth oxides (99.9% purity) with ammonium chloride of regante grade and purified by sublimation [13]. Impurities of the purified crystals were analysed by emission spectrography and X-ray fluorescence spectrometry. The impurity contents were almost the same as those reported previously [14–17]. The molar volumes of the melts were measured dilatometrically with the same apparatus as described in [18]. DTA was used for the measurement of melting points. The measurements were carried out, using $\alpha\text{-Al}_2\text{O}_3$ as reference material, with a cooling rate of 7–11 °C/min. The DTA apparatus was calibrated with the melting points of pure Ag, Al, Zn, and Pb.

Figure 1 shows the molar volumes of the molten chlorides expressed as linear functions of the temperature obtained by a least squares fit of the data. Table 1 gives the parameters of these functions. The obtained melting points are listed in Table 2 together with those reported in

the literature [2–9]. Our results are close to those measured by Spedding and Daane [3].

The crystal structure of the rare earth chlorides has been classified into two groups: the chlorides from LaCl_3 to GdCl_3 are hexagonal with the space group $\text{P6}_3/\text{m}(\text{C}_{6h}^2)$ [10, 12], and DyCl_3 and YCl_3 are monoclinic with $\text{C2/m}(\text{C}_{2h}^3)$ [11]. From these crystal data the molar volumes can be calculated by the equations

$$V_h = (\sqrt{3}/2) \times a^2 c \times N/Z \quad (1)$$

and

$$V_m = abc \times \sin B \times N/Z. \quad (2)$$

where V is the molar volume in $\text{cm}^3 \text{mol}^{-1}$ (subscripts h and m mean hexagonal and monoclinic, respectively), a , b , and c are the lattice constants, N is Avogadro's number, B the angle between the two axes in the monoclinic crystal, and Z the number of stoichiometric units contained in the unit cell. The results are shown in Table 3. The molar volume of the hexagonal chlorides decreases slightly with increasing atomic number due to the lanthanide contraction. According to Fig. 1, the molar volume at a given temperature of these chlorides in the liquid state appears to increase with increasing atomic number. However, the molar volumes of these molten chlorides at their melting points, as obtained by an extrapolation by means of the molar volume equations, were found to give the same tendency as those of the solids (cf. Table 3).

The per cent volume changes on melting of the chlorides were calculated from the values of V_s and V_m in Table 3. The thermal expansion of these solids being not known but very small, the V_s values at room temperature have been taken. The results are listed in column 5 of Table 3. For the hexagonal chlorides, large volume increases were observed, its order seeming to follow the order of the atomic

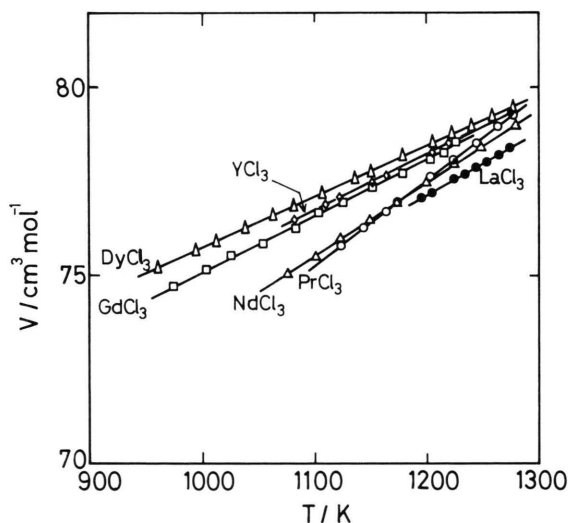


Fig. 1. Molar volumes of some molten rare earth chlorides.

Reprint requests to Prof. J. Mochinaga, Department of Synthetic Chemistry, Faculty of Engineering, Yayoi-cho, Chiba-shi, Chiba 260, Japan.

Table 1. Molar volume equations of molten pure rare earth chlorides.

$V = a + b \times T, \quad V/\text{cm}^3 \text{mol}^{-1}, T/\text{K}$		
Salt	a	$b \times 10$
LaCl ₃	56.76	0.1699
PrCl ₃	47.70	0.2512
NdCl ₃	54.31	0.1909
GdCl ₃	60.90	0.1422
DyCl ₃	61.70	0.1399
YCl ₃	61.08	0.1427

Table 2. Melting points (in K) of rare earth chlorides. This work and literature.

Salt	This work	[2]	[3]	[4]	[5]	[6]	[7]	[8]	[9]
LaCl ₃	1150	1125	1135		1143	1119	1135	1123	
PrCl ₃	1059	1059	1059	1039	1096				
NdCl ₃	1029	1033	1031	1013	1033	1031			
GdCl ₃	875	882	875	863	875	866			
DyCl ₃	928	927	920	898	920				
YCl ₃	987	973	982		973				987

number. On the other hand, for the monoclinic DyCl₃ and YCl₃, the volume changes very little on melting. This behavior of the chlorides studied has also been reported by Cho et al. [19].

In the hexagonal solid chlorides, the rare earth metal ions are surrounded by nine chloride ions with two different distances [10, 12]. On the other hand, the metal ions in the monoclinic DyCl₃ and YCl₃ are surrounded by six chloride ions with three different distances [11]. The fact that the chlorides from LaCl₃ to GdCl₃ show a large volume increase on melting suggests that the nearest ionic distances and the number of ions in the first coordination shell decrease significantly on fusion, similar to the alkali halides [1]. The short range arrangement in molten CaCl₂ with little volume change on melting is known to be close to that of the crystal [20–22]. Also the short range arrangement in liquid DyCl₃ and YCl₃ is expected to be close to that in the corresponding solid.

Table 3. Molar volumes of some rare earth chlorides.

Salt	mp/K	V_s	V_m	ΔV (%)
LaCl ₃	1150	63.90	76.30	19.1
PrCl ₃	1059	61.40	74.30	21.0
NdCl ₃	1029	60.47	73.65	21.8
GdCl ₃	875	58.03	73.34	26.4
DyCl ₃	928	74.38	74.62	0.3
YCl ₃	987	74.83	75.17	0.5

V_s and V_m are the molar volumes of the solid at room temperature and the melt at the mp., respectively, in $\text{cm}^3 \text{mol}^{-1}$.

- [1] K. Furukawa, Discuss. Faraday Soc. **32**, 53 (1961).
- [2] R. E. Thoma, The Rare Earth Halides, in: Progress in the Science and Technology of the Rare Earth (L. Eyring, ed.), Vol. 2, p. 90. Pergamon Press, London 1966.
- [3] F. H. Spedding and A. H. Daane, Met. Revs. **5**, 297 (1960).
- [4] K. Cho and T. Kuroda, Denki Kagaku **40**, 837 (1972).
- [5] G. J. Janz, F. W. Dampier, G. R. Lakshminarayanan, P. K. Lorenz, and R. P. T. Tomkins, Molten Salts, Vol. 1, NSRDS-NBS 15, Nat. Bur. Stand. 1968, p. 52.
- [6] G. Vogel and A. Schneider, Inorg. Nucl. Chem. Lett. **8**, 513 (1972).
- [7] T. Kuroda, Denki Shikenjyo Houkoku **561**, 45 (1957).
- [8] I. S. Morozov, Z. N. Shevtsova, and L. V. Klyukina, Zhur. Neorg. Khim. **2**, 1640 (1957).
- [9] G. N. Papatheodorou, J. Chem. Phys. **66**, 2893 (1977).
- [10] D. H. Templeton and C. H. Dauben, J. Amer. Chem. Soc. **76**, 5237 (1954).
- [11] D. H. Templeton and G. F. Carter, J. Phys. Chem. **58**, 940 (1954).
- [12] B. Morosin, J. Chem. Phys. **49**, 3007 (1968).
- [13] J. Mochinaga, K. Igarashi, and S. Ueda, Asahi Garasu Kougyou Gijutu Shoureikai Kenkyuu Houkoku **25**, 135 (1975).
- [14] J. Mochinaga, H. Ohtani, and K. Igarashi, Denki Kagaku **49**, 19 (1981).
- [15] J. Mochinaga, K. Igarashi, T. Aoki, and Y. Iwadate, Bull. Chem. Soc. Japan **51**, 3107 (1978).
- [16] Y. Sasaki, K. Igarashi, and J. Mochinaga, Denki Kagaku **50**, 226 (1982).
- [17] Y. Iwadate, K. Igarashi, J. Mochinaga, and T. Adachi, J. Electrochem. Soc. **133**, 1162 (1986).
- [18] K. Igarashi, Y. Iwadate, and J. Mochinaga, Z. Naturforsch. **40a**, 520 (1985).
- [19] K. Cho, K. Irisawa, J. Mochinaga, and T. Kuroda, Electrochim. Acta **17**, 1821 (1972).
- [20] S. Biggin and J. Enderby, J. Phys. C **14**, 3577 (1981); S. Biggin and J. Enderby, J. Phys. C **15**, L 305 (1982).
- [21] S. Iwamoto, N. Umesaki, T. Asahina, and M. Kosaka, J. Chem. Soc. Japan **1982**, 920.
- [22] K. Igarashi, T. Nijima, and J. Mochinaga, Proc. First Int. Symposium on Molten Salt Chem. and Technol. Molten Salt Committee of The Electrochemical Society of Japan 1983, p. 469.